

P303L Stainless Steel

DESCRIPTION

P303L is a free machining, austenitic grade that offers moderate corrosion resistance. This stainless steel is sintered in either a partial vacuum or a hydrogen atmosphere to improve ductility and corrosion resistance. P303L is a sulfurized grade that is an excellent option for parts that require secondary machining operations, such as food service equipment, pump components and non-magnetic housings.

ADDITIVES

303L can also be admixed with MnS or MoS₂ for added machinability.



PRODUCT	POWDER PROPERTIES		COMPACTING PRESSURE (TSI)	GREEN STRENGTH (PSI)	GREEN DENSITY (GM/CC)	SINTERED DENSITY (GM/CC)	SINTERED BREAKING STRENGTH (PSI)	DIMENSIONAL CHANGE FROM DIE SIZE (%)	UTS (PSI)	% ELONG	RB HARDNESS (APPARENT)
	APPARENT DENSITY (GM/CC)	FLOW (SEC./50G)									
P303L	2.8	30	30	380	6.23	6.33	71,000	-0.54	41,000	3.4	41.0
			40	900	6.50	6.60	91,000	-0.44	51,000	4.8	50.0
			50	1030	6.70	6.75	109,000	-0.40	54,000	5.8	68.0

Compacting properties were measured on powder blended with 1% lithium stearate. Sintering was done in dissociated ammonia at 2050°F for 45 minutes.

The data herein are subject to revision without notice. Since AMETEK products, and the information given and recommendations made herein, may be used under conditions beyond our control, AMETEK makes no guarantee, either express or implied, concerning the sustainability of our products, or the applicability and accuracy of the information, or recommendations, in any specific situation. User is solely responsible for determining the suitability of AMETEK products of any specific purpose.

P303L Stainless Steel

POWDER PROPERTIES

Chemical Composition






Chromium: 17-19%
 Nickel: 8-13%
 Manganese: 2% max
 Silicon: 1% max
 Sulfur: 0.15-0.30%
 Carbon: 0.03% max
 Phosphorus: 0.045% max
 Iron: Balance

Physical Properties

Apparent Density: 2.8 g/cm³
 Flow Rate: 30 sec/50g

SINTERED PROPERTIES

Sintered properties were determined using test specimens that were sintered for 45 minutes in dissociated ammonia with a -40°F dew point.

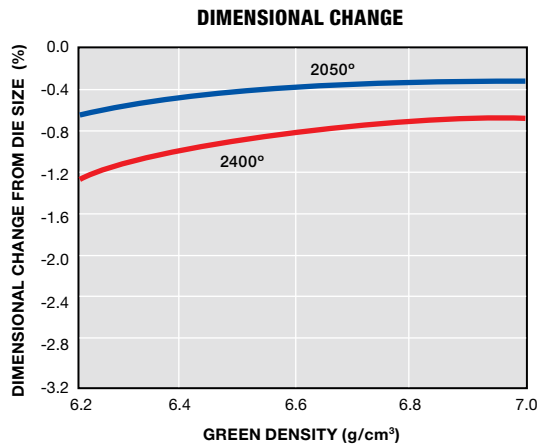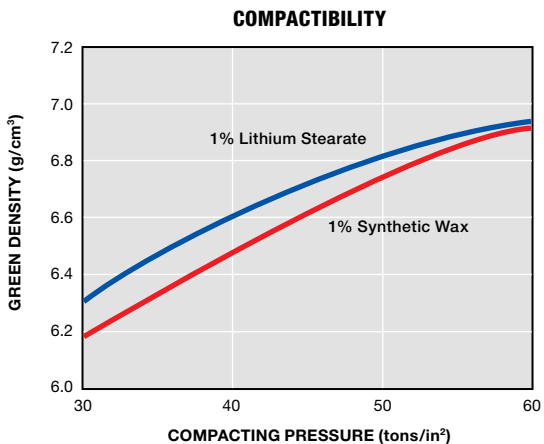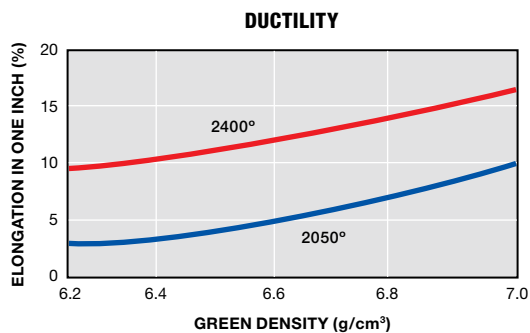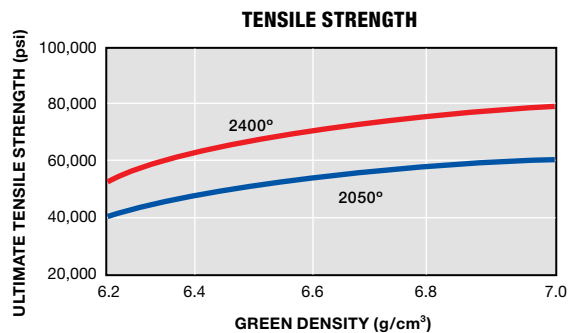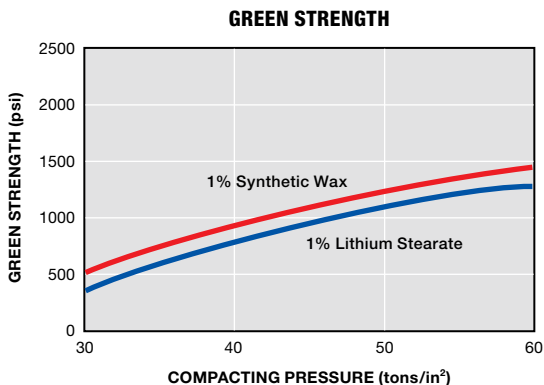

1085 Route 519 • Eighty Four, PA 15330 USA • Tel: 724-225-8400 • Fax: 724-225-6622
 E-mail: EF.Sales@ametek.com

www.ametekmetals.com

©2018 by AMETEK, Inc. All rights reserved.