

304L POWDER STAINLESS STEEL

TECHNICAL DATA SHEET

DESCRIPTION

304L is a corrosion resistant material that exhibits good property stability below 1000°F. 304L is often the most practical stainless steel choice for parts that need the benefit of an austenitic grade. 304L exhibits better overall corrosion resistance than 303L.

This material is a good choice for parts that will not be subjected to demanding machining operations. A major benefit of this material is the balance of good material performance and economical cost.

PRODUCT	POWDER PROPERTIES		COMPACTING PRESSURE (TSI)	GREEN STRENGTH (PSI)	GREEN DENSITY (GM/CC)	SINTERED DENSITY (GM/CC)	SINTERED BREAKING STRENGTH (PSI)	DIMENSIONAL CHANGE FROM DIE SIZE (%)	UTS (PSI)	% ELONG	RB HARDNESS (APPARENT)
	APPARENT DENSITY (GM/CC)	FLOW (SEC./50G)									
304L	2.7	30	30	410	6.25	6.33	73,000	-0.53	40,000	3.4	40.0
			40	900	6.50	6.60	94,000	-0.44	50,000	4.2	49.0
			50	1120	6.70	6.80	115,000	-0.39	56,000	5.4	68.0


Compacting properties were measured on powder blended with 1% lithium stearate. Sintering was done in dissociated ammonia at 2050°F for 45 minutes.

POWDER PROPERTIES


CHEMICAL COMPOSITION			
Chromium	18 - 20%	Carbon	0.03% max
Nickel	8 - 12%	Sulfur	0.03% max
Manganese	2% max	Phosphorus	0.045% max
Silicon	1% max	Iron	Balance

PHYSICAL PROPERTIES	
Apparent Density	2.8 g/cm ³
Flow Rate	30 sec/50g

GREEN STRENGTH

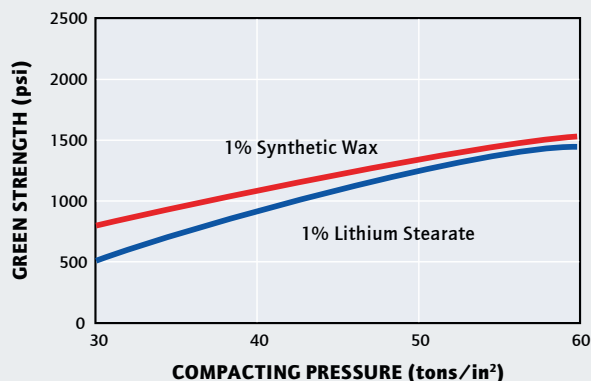

COMPACTIBILITY



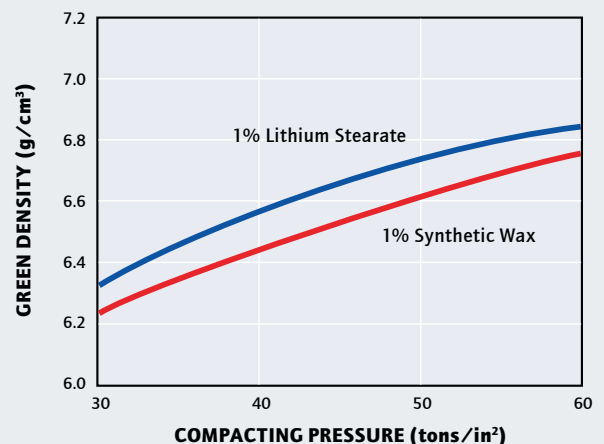


304L POWDER STAINLESS STEEL

TECHNICAL DATA SHEET

SINTERED PROPERTIES

Sintered properties were determined using test specimens that were sintered for 45 minutes in dissociated ammonia with a -40°F dew point.

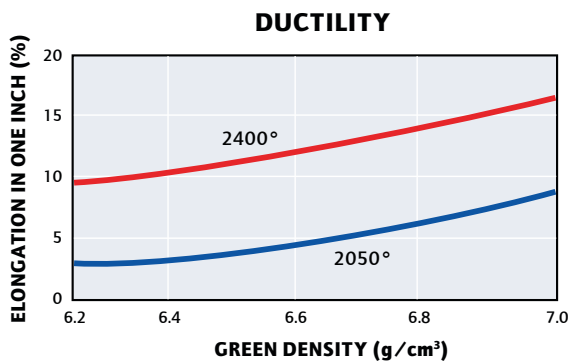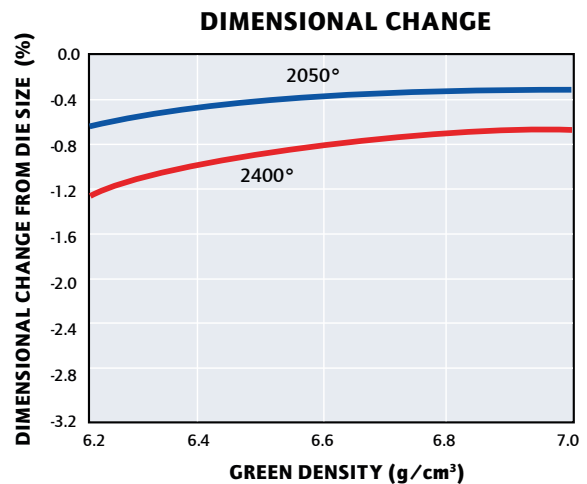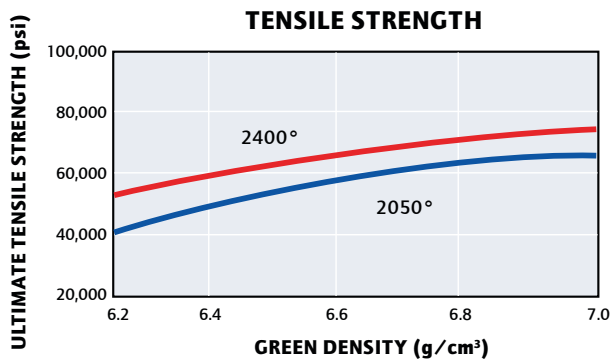

1085 Route 519, Eighty Four, PA 15330, United States
E: EF.sales@ametek.com | T: (+1) 724-225-8400

www.powderclad.com

The data herein are subject to revision without notice. Since AMETEK products, and the information given and recommendations made herein, may be used under conditions beyond our control, AMETEK makes no guarantee, either express or implied, concerning the sustainability of our products, or the applicability and accuracy of the information, or recommendations, in any specific situation. User is solely responsible for determining the suitability of AMETEK products of any specific purpose.